

CSIRO ACOUSTIC MEASUREMENT REPORT

Commonwealth Scientific and Industrial Research Organisation, Infrastructure Technologies Acoustics Testing Laboratory, Gate 5, 2 Normanby Road, Clayton, Vic 3168 Australia

Report No: AC287-08-1

Client:

Bailey Interiors Pty Ltd

83-85 Boundary Road, Mortdale, NSW 2223

Measurement Type: Sound Absorption

AS ISO 354-2006 [R2016]: Acoustics-Measurement of sound absorption in a reverberation room AS ISO 11654-2002 [R2016] (ISO 11654:1997): Acoustics-Rating of sound absorption-Materials and systems

Test Specimen [Specimen area: 3.6 x 3.0 m (10.8 m²), Test configuration: Type E-200]

Description: • Bailey "EcoCheck" ceiling tiles, • direct-fix type,

with integral glass fibre batts (batts open to ceiling cavity at rear)

Tile Details3

- Perforated moulded plaster ceiling tiles, nominal size 600 x 600 mm (x 30 mm thick) designed to be nail/screw fixed to overhead ceiling battens.
- Manufactured with an integral glass fibre batt (Bradford Supertel, ≈42 kg/m³, 20 mm thick) behind the perforated face, constrained around the perimeter at the rear with plaster skim-coat covering the outer 60 mm of the batt (approx).
- Perforated with a regular pattern of 6.5 mm dia holes (2888 count); the holes near the edges being closed at the rear, the remaining holes opening into the glass fibre batt behind.

 Open area percentage⁴ (estimated): 21.3% (only holes open front and back); 26.6% (all holes).

- The test specimen was installed as an upside-down ceiling on the floor of the chamber.
- A 200 mm deep enclosure (32 mm MDF timber, approx 23 kg/m², built to surround an area of 3600 x 3000 mm) was placed on the floor of the chamber at an 11° angle to the chamber walls (not parallel, as per AS ISO 354 cl 6.2.1.2). Two modules (each 100 mm deep) were stacked to create the F-200 enclosure
- · A system of plastic support feet sitting on aluminium extrusions (upside-down Tees) was set up inside the enclosure to support the tiles with their exposed face nominally flush with the enclosure. The cavity behind was a single undivided cavity without internal partitions.
- Tiles were arranged in a 6 x 5 array on the support system.
- All relevant joins in the installation were taped to close off any gaps ie the junctions of the enclosure modules to each other, to the floor, and to the tile array, and where adjacent tiles butted against each other in the installed array.
- Specimen installation was carried out by laboratory staff.




Test specimen installed for testing (image inverted to depict ceiling installation)





Tile details - Left: whole tile, Right: close-up view

Measurement Details & Results							
	Freq	Absorpt	Absorption coefficients			Reverberation times, T ₆₀ (sec)	
	Hz	Cίs	α_{p}	95% Conf (δ)	Empty room	with Specimen	
	100	0.35		0.05	5.38	3.32	
	125	0.24	0.40	0.06	6.05	4.08	
	160	0.63		0.08	6.60	2.77	
	200	0.75		0.12	5.89	2.39	
	250	0.91	0.80	0.11	4.87	1.98	
	315	0.79		0.06	5.92	2.32	
	400	0.77		0.05	5.89	2.35	
	500	0.75	0.75	0.05	5.64	2.35	
	630	0.77		0.05	5.34	2.26	
	800	0.79		0.05	5.14	2.19	
	1000	0.86	0.85	0.04	4.89	2.05	
	1250	0.94		0.04	4.40	1.86	
	1600	0.89		0.04	3.91	1.82	
	2000	0.79	0.80	0.04	3.58	1.85	
	2500	0.70		0.03	3.15	1.82	
	3150	0.59		0.03	2.73	1.78	
	4000	0.55	0.55	0.05	2.21	1.57	
	5000	0.49		0.05	1.78	1.37	

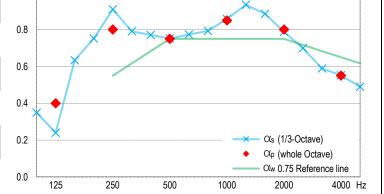

Performance Indices 1,2

 $\alpha_{\rm W} = 0.75 \, (L)$ SAA = 0.81NRC = 0.85

The required 12 spatially independent decay curves came from ensemble averaging 10 successive decays with each of 3 different source loudspeaker positions, all sampled by 4 fixed microphones, using linear averaging.

Date of measurement: Temperature & humidity: Atmospheric pressure

Empty room 1 Jun 2021 16 °C. 51 % R.H. 1008 mBar

Measurement Conditions

with Test Specimen 1 Jun 2021 17 °C, 48 % R.H. 1008 mBar

Notes, Deviations etc

- Shape indicators (L, M, and H), if any, following the Cw index, indicate α_p values above the reference contour by ≥ 0.25 in the Low, Medium or High frequency ranges respectively; it is strongly recommended to use this single number rating in combination with the complete sound absorption coefficient curve.
- SAA and NRC are defined in ASTM C423; laboratory requirements for which differ from AS ISO 354.
- Physical characteristics of materials may be as per client or supplier's advice; not necessarily verified by CSIRO.
- Open area estimates are based on 600 x 600 mm of ceiling area being 'treated' by each tile.

1.2

1.0

Issuing Authority

Signed David Truett Date 25 June 2021

Instrumentation

Real time analyser: • Brüel & Kjær PULSE LAN-XI type 3160-A-4/2

Microphones/preamps: • 4 microphones (1 x B&K 4134, 1 x B&K 4166, and 2 x GRAS 40AR)

on B&K and GRAS preamps, in fixed positions as per AS ISO 354 Noise source: • Room populated with three Norsonic NOR276 dodecahedron

loudspeakers, driven in turn by a Norsonic NOR280 power amplifier.

Calibration: • Analyser: July 2018 (NATA cal)

Laboratory Construction

Reverb room: • 300 mm thick concrete (closed off from the adjoining room by an MDF wall) • parallelepiped with dimensional proportions 1:1.3:1.6 for

distribution of room modes • approx 202 m³ total room volume approx 215 m² surface area excluding diffusers

Diffusers: • 20 stationary diffusers, approx 40 m² total surface area Absorption area: • in accordance with AS ISO 354, unless noted otherwise

Legal Information and Disclaimer Copyright @ 2021 CSIRO. To the extent permitted by law, CSIRO (including its employees and consultants) excludes all liability to any person for any consequences, including but not limited to all losses, damages, costs, expenses and any other compensation, arising directly or indirectly from using any information or material contained in this document. Reports relate only to items tested. No alterations permitted. This report may be distributed only in its entirety. Page 1 of 1